

Magnetic Order in Lightly Doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$

A. Gozar,^{1,2,*} B. S. Dennis,¹ and G. Blumberg^{1,†}

¹*Bell Laboratories, Lucent Technologies, Murray Hill, New Jersey 07974, USA*
²*University of Illinois at Urbana-Champaign, Urbana, Illinois 61801-3080, USA*

Seiki Komiya and Yoichi Ando

Central Research Institute of Electric Power Industry, Komae, Tokyo 201-8511, Japan
(Received 19 August 2003; published 6 July 2004)

We study long wavelength magnetic excitations in lightly doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ($x \leq 0.03$) detwinned crystals. The lowest energy magnetic anisotropy induced gap can be understood in terms of the antisymmetric spin interaction inside the antiferromagnetic (AF) phase. The second magnetic resonance, analyzed in terms of in-plane spin anisotropy, shows unconventional behavior within the AF state; it led to the discovery of collective spin excitations pertaining to a field induced magnetically ordered state. This state persists in a 9 T field to more than 100 K above the Néel temperature in $x = 0.01$.

DOI: 10.1103/PhysRevLett.93.027001

PACS numbers: 74.25.Gz, 74.72.Dn, 75.30.Gw, 78.30.Am

At short wavelengths, the spin excitations in underdoped 2D cuprates are governed by the large antiferromagnetic (AF) superexchange, $J \approx 145$ meV, while in the long wavelength limit the magnetic energy scales are set by small anisotropy parameters [1–3]. In spite of the relative weakness, the impact of the low energy magnetism on the carrier and lattice dynamics in detwinned $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ crystals has been shown recently to be unexpectedly large. Magnetic susceptibility data show a persistent spin anisotropy even outside the AF region [4], while the transport properties revealed besides a sizable anisotropy of the in-plane dc resistivity [5] also a large low temperature magnetoresistance [6]. These effects call for an investigation of long wavelength magnetic excitations using a high resolution probe. A magnetic field study is of particular interest due to the surprising discovery in $x = 0.01$ $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ at room temperature of magnetic field induced structural changes [7], phenomenon which makes this compound unique because of the existence of strong AF correlations.

Underdoped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ crystals are slightly orthorhombic below 300 K and long range AF order exists for $x \leq 0.02$. The layered structure allows for a XY spin anisotropy which in the spin-wave approximation leads to an out-of-plane polarized gap, Δ_{XY} [8]. The in-plane orthorhombicity and the spin-orbit coupling lead to an antisymmetric Dzyaloshinskii-Moriya (DM) spin interaction in the CuO planes which gaps the remaining Goldstone mode and leads to a second in-plane polarized gap, Δ_{DM} , at $k = 0$ [8]. The same spin-orbit interaction also allows the Raman coupling to one-magnon excitations [9]. Each CuO plane has a weak perpendicular magnetic moment due to the DM interaction, but the interplane exchange orients these moments antiferromagnetically as shown in Fig. 1(a). An external magnetic field $\vec{H} \parallel \hat{c}$ leads to a weak-ferromagnetic (WF) transition [6,10] depicted in Fig. 1(b).

In this Letter, we study low energy Brillouin zone center magnetic dynamics in lightly doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ as a function of doping, temperature, and magnetic field. Two magnetic modes are observed in the AF phase. The one at lower energies is the spin-wave gap induced by the antisymmetric DM interaction, and its anisotropic properties in magnetic field can be well explained using a canonical form of the spin Hamiltonian. A new finding is a magnetic field induced mode (FIM) whose dynamics allows us to discover a spin ordered state outside the AF order which is shown to persist in a 9 T field as high as 100 K above the Néel temperature T_N in $x = 0.01$. We propose for the field induced magnetic order a state with a net WF moment in the CuO plane and analyze the FIM in the context of in-plane magnetic anisotropy.

Detwinned single crystals of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ with $x = 0-0.03$ were grown as described in [4]. The Néel temperatures for the $x = 0$ and 0.01 crystals studied here are 310 and 215 K, respectively, in zero field, and a decrease of

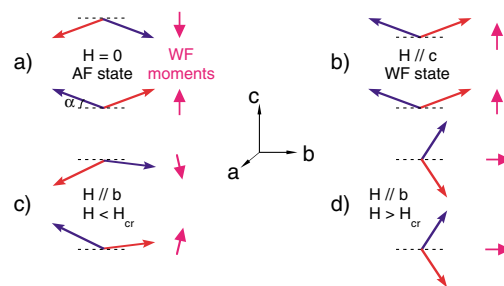


FIG. 1 (color online). Cartoon showing spin orientations in two adjacent CuO planes. (a) The 3D AF arrangement in zero applied field and the corresponding orientation of the WF moments in each plane. The canting angle α from the CuO planes is exaggerated. (b) The WF state. (c) Spin configuration for small fields $\vec{H} \parallel \hat{b}$. (d) The proposed spin ordering obtained by further increasing the field $\vec{H} \parallel \hat{b}$ in (c).

T_N on the average by 1 K/T (for $x = 0$) and almost 4 K/T (for $x = 0.01$) is observed for fields $\vec{H} \parallel \hat{b}$. We use the notation of the $Bmab$ structure for crystallographic axes. We denote by $(e_{in}e_{out})$ polarization configurations, with $e_{in/out}$ the direction of the incoming/outgoing photons. (RL) and (RR) denote circular polarizations. The crystals were mounted in a continuous flow optical cryostat and the Raman data were taken with incident photon power of a few mW and $\lambda = 647.1$ nm focused onto (ab) crystal surfaces. The magnetic field data were taken with the cryostat inserted into the horizontal bore of a superconducting solenoid.

Figure 2 shows data from La_2CuO_4 at 10 K for three directions of the external magnetic field. A sharp resonance is observed in zero field at 17 cm^{-1} . This resonance disperses upwards (downwards) for $\vec{H} \parallel \hat{a}$ ($\vec{H} \parallel \hat{b}$). For

the $\vec{H} \parallel \hat{c}$ axis, the mode disperses downwards until $H_{WF} \approx 6\text{ T}$, where the transition to the WF state [Fig. 1(b)] takes place [6,10]. In the 6–7 T range, the resonance remains around 15 cm^{-1} but decreases in intensity with a concomitant appearance of another feature around 21 cm^{-1} . In Figs. 2(e) and 2(f), we show hysteretic loops for the 21 and 15 cm^{-1} modes intensities, very similar to the behavior of the (100) and (201) magnetic Bragg peaks [12], reflecting the dynamics of magnetic domains in the presence of small crystalline imperfections.

The nature of the mode shown in Fig. 2 can be understood by analyzing the spin Hamiltonian [8]

$$\mathcal{H} = \sum_{\langle i,j \rangle} [(J + \alpha)\vec{S}_i\vec{S}_j - \alpha S_i^z S_j^z + \vec{d}(\vec{S}_i \times \vec{S}_j)] - \vec{H} \sum_i \vec{S}_i, \quad (1)$$

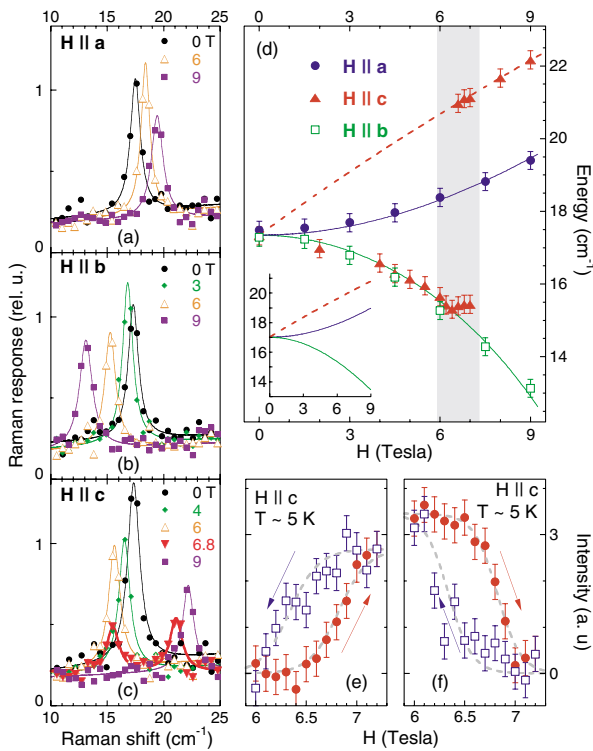


FIG. 2 (color online). Panels (a)–(c) show 10 K (RL) polarized Raman spectra of the DM gap in La_2CuO_4 with the external field \vec{H} parallel to the a , b , and c axes. Solid lines are Lorentzian fits. In (c), the 6.8 T spectrum shows the coexistence of the AF and the WF states. (d) shows the field dependence of Δ_{DM} for $\vec{H} \parallel \hat{a}$ (circles), $\vec{H} \parallel \hat{b}$ (squares), and $\vec{H} \parallel \hat{c}$ (triangles). The $\vec{H} \parallel \hat{c}$ data show the transition to the WF state depicted in Fig. 1(b). The continuous lines are fits with $\sqrt{\Delta_{DM}^2 + \gamma H^2}$ [$\Delta_{DM} = 17.35 \pm 0.25\text{ cm}^{-1}$, $\gamma_{H||a} = 0.96$, and $\gamma_{H||b} = -1.65\text{ (cm T)}^{-2}$] and the dashed line is a fit to the form $\sqrt{\Delta_{DM}^2 + \beta H}$ [$\beta = 22.6\text{ cm}^{-2}\text{ T}^{-1}$]. Hysteretic loops of the lower (e) and higher (f) energy DM gaps at the WF transition [shaded area in (d)]. Grey dashed lines in (e) and (f) are guides for the eye. The inset in (d) shows the results of a semiclassical calculation of the DM gap dispersions as described in the text (see also [11]).

where J , α , \vec{d} , \vec{H} , and \vec{S}_i are the isotropic Heisenberg exchange, the in-plane anisotropy, the DM vector, the external field, and the spin on lattice site i . We calculated the dispersion of the $k = 0$ spin-wave modes for different magnetic field orientations at $T = 0\text{ K}$ by minimizing \mathcal{H} and linearizing the equations of motion [11]. The inset of Fig. 2(d) shows the behavior of the DM gap assuming a full moment on Cu sites, $\vec{d} \parallel \hat{a}$ and $\Delta_{DM} = 17\text{ cm}^{-1}$. The agreement between the experimental data and the calculation is quantitative allowing us to assign this mode to Δ_{DM} and to confirm the validity of the spin-wave approximation. The similar field dispersion for $\vec{H} \parallel \hat{b}$ and $\vec{H} \parallel \hat{c}$ ($H < H_{WF}$) is intriguing because the model does not have rotational symmetry with respect to the a axis. The energy of the DM gap is also in agreement with the value inferred from inelastic neutron scattering (INS) measurements [2,13]. Its softening for $\vec{H} \parallel \hat{b}$ explains the decrease of T_N and implies the possibility of a magnetic instability by further increasing the field in this configuration. In principle, our data allows also for a quantitative estimation of the magnitude of other higher order spin interactions [3,14] from magnetic gap renormalization effects. Using the expressions $\Delta_{DM} = 2.34d$ [1,3], we obtain for La_2CuO_4 the value $d = 0.92 \pm 0.013\text{ meV}$.

Doping and temperature dependent properties of the DM gap are shown in Fig. 3. Figure 3(a) shows the gap as a function of doping at 10 K. We observe that the DM gap is present only in the AF ordered region of the phase diagram. The gap resonance found at 12.5 cm^{-1} in $x = 0.01$ remains sharp but is weaker and has a strongly renormalized energy compared to the undoped case. As a function of temperature, the gap excitation disappears below 5 cm^{-1} as we approach T_N , which is indicative of a conventional magnetic soft-mode behavior [Figs. 3(b) and 3(c)]. The observed homogeneous renormalization with doping of the DM gap energy at 10 K from $x = 0$ to $x = 0.01$ rules out a possible macroscopic phase separation into $x \approx 0$ and $x \approx 0.02$ regions suggested in Ref. [15]. Since the DM interaction is induced by lattice

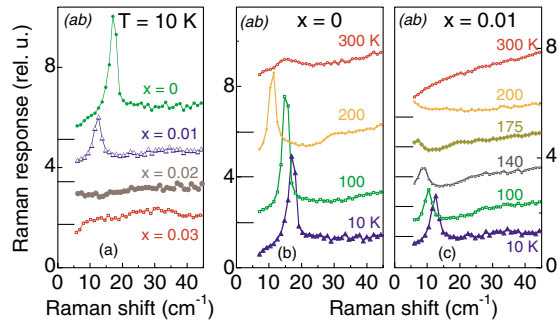


FIG. 3 (color online). Doping and temperature dependence of the DM gap in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ in (ab) polarization for zero applied field. (a) 10 K data for $x = 0 - 0.03$. (b),(c) Temperature dependent Raman spectra for $x = 0$ and 0.01. Data are vertically offset.

orthorhombicity, the decrease of almost 30% at $T = 10$ K for the gap value between $x = 0$ and 0.01 is surprising compared to the much smaller decrease in the orthorhombicity and relates it to strong sensitivity to hole doping. Our data suggest that the antisymmetric exchange interaction is strongly competing with frustration and associated spin distortions induced by hole doping [16,17].

In Fig. 3(b), there is a broad peak at 300 K around 15 cm^{-1} for $x = 0$ which becomes a kink around 25 cm^{-1} at 200 K and disappears with further cooling. The effects of magnetic fields on this excitation for La_2CuO_4 are shown in Fig. 4. At 10 K, we observe for finite $\vec{H} \parallel \hat{b}$ a FIM around 40 cm^{-1} which is sharp and hardens slightly up to 9 T. At 230 K, the FIM is broader and it softens with increasing field gaining spectral weight from the lower energy side. At 300 K, we observe qualitatively similar behavior as at 230 K for $H \leq 6$ T, and beyond that value we see the emergence of two independent peaks which

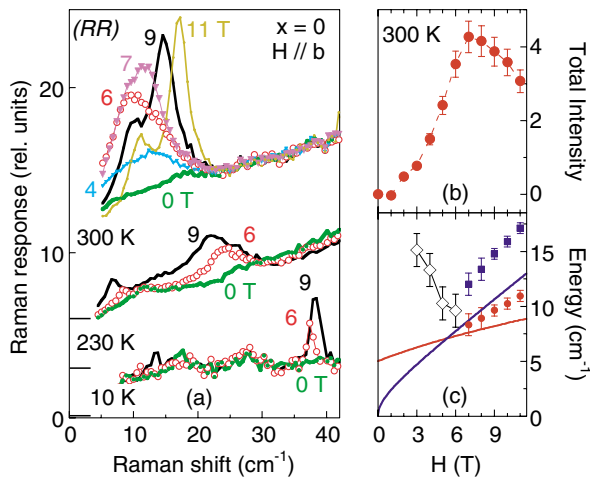


FIG. 4 (color online). (a) Magnetic field dependence of (RR) polarized spectra in La_2CuO_4 at several temperatures. Data are vertically offset. Integrated intensities obtained by subtracting the 0 T spectrum in (a) from finite field data, panel (b), and the energies, panel (c), of the magnetic modes at 300 K. The lines in (c) are calculated using Eq. (1) with $\alpha = 0$ (see text).

027001-3

harden further with field [see Fig. 4(c)]. Figure 4(b) shows the total integrated intensity of the magnetic modes at a given field. The FIMs are seen only for fields $\vec{H} \parallel \hat{b}$.

In La_2CuO_4 the FIM dynamics marks two events. The first seems to be a phase transition at 300 K and fields around 6 T. This is indeed the case because we know that the Néel temperature in La_2CuO_4 is around 310 K and that the magnetic susceptibility χ_b shows T_N decreasing at a rate of about 1 K/T. Moreover, the narrow widths of the magnetic excitations above 6 T ($2 \text{ cm}^{-1} \approx 0.25 \text{ meV}$) at temperatures more than 2 orders of magnitude higher ($300 \text{ K} \approx 25 \text{ meV}$) argue strongly for the collective nature of these excitations which correspond to another magnetically ordered state with a well-defined gap in the excitation spectrum. The second event, a crossover taking place between 230 and 10 K, is reflected in the opposite dispersion with field and different peak widths at these two temperatures. As for the doping dependence, except for a much weaker intensity (see Fig. 5), we observed the same qualitative behavior in $x = 0.01$ $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$. The FIM is not seen (in fields up to 9 T) at any temperature for $x \geq 0.02$.

Figure 5 shows temperature dependent (RR) polarized spectra in a 9 T field $\vec{H} \parallel \hat{b}$ for $x = 0$ and 0.01. The crossover in La_2CuO_4 takes place around 150 K, the temperature below which the FIM width narrows. Figure 5(c) shows that the intensity of this excitation increases as we approach T_N , and that around 300 K we

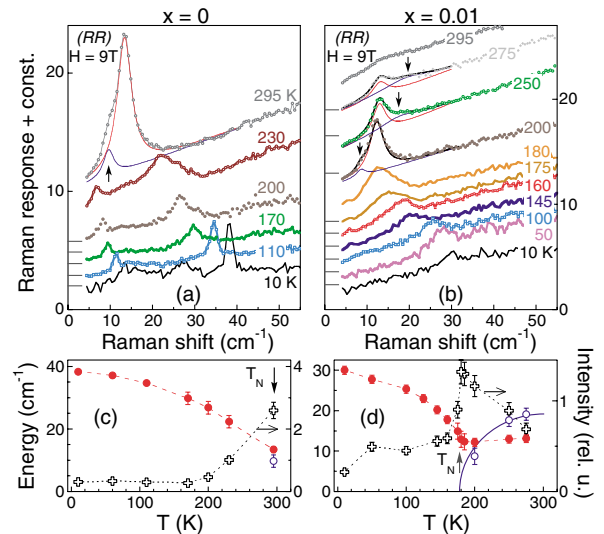


FIG. 5 (color online). Temperature dependence of the field induced mode (FIM) in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ for $x = 0$ (left) and 0.01 (right). (a),(b) Data (vertically offset) in (RR) polarization for $\vec{H} \parallel \hat{b}$ at 9 T. The continuous lines for $T = 295$ K in (a), $T = 250$, and 275 K in (b) are two-Lorentzian fits to the data. (c),(d) Variation with temperature of the FIM energies (circles, left scales) and intensities (crosses, right scales). Empty circles correspond to the arrows in (a),(b). The blue solid line in (d) is a guide for the eye. We also show by arrows the Néel temperatures for $\vec{H} \parallel \hat{b}$ at 9 T in the two samples.

027001-3

observe the splitting due to the occurrence of the field induced ordering.

The temperature dependence of the FIM across the Néel boundary can be studied in the $x = 0.01$ crystal which has a lower T_N . At 9 T and below 180 K, the behavior for $x = 0.01$ is very similar to that in the undoped crystal showing a softening of the FIM as we warm to T_N . The 200 K data show that the FIM has, similarly to the 295 K data for $x = 0$, a low energy shoulder. We believe that this weak excitation is the softened peak marked by arrows at 250 and 275 K where the data shows the coexistence of two peaks. The lowering in energy can be naturally explained in terms of soft-mode behavior above the magnetic transition while below T_N this mode becomes the DM gap in Fig. 3(c). The two peaks above 180 K in $x = 0.01$ $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$, which correspond in La_2CuO_4 to the two features seen in Fig. 4(c) above 6 T, show that at 9 T the new magnetic order extends up to about 100 K above T_N . In comparison, the strong feature at 200 K situated at 12 cm^{-1} hardens only slightly with increasing temperature [see Fig. 5(d)]. This panel also shows that the intensity of the FIMs is peaked at T_N , which is unexpected in a conventional picture where intensities of long wavelength gap modes scale with the AF order parameter as T_N is approached from below [13].

A possible explanation for the FIM is its identification to the XY gap. Support for this assignment is the presence of this mode only in $x = 0$ and $0.01\text{ La}_{2-x}\text{Sr}_x\text{CuO}_4$ as well as the comparison to INS data [2,13] which estimates $\Delta_{XY} \approx 40\text{ cm}^{-1}$ at 10 K. Equation (1), which described well the DM gap, is also in support because it predicts (at $T = 0\text{ K}$) a shift of about 6% of the XY gap from 0 to 9 T, consistent with the small hardening we observe at 10 K in Fig. 4(a). As to the nature of the induced order, we propose a state similar to the one depicted in Fig. 1(d). This is suggested by the magnetic susceptibility data which shows that the moments on Cu sites remain confined in the (bc) plane above T_N [4] and also by recent magnetoresistance measurements [6] which are consistent with a gradual rotation of the WF moments. A departure from a two-step transition [18] with an a -axis spin-flop process occurring between the states shown in Figs. 1(c) and 1(d) is expected because the susceptibility χ_a is the smallest below 300 K for $x = 0$ and 0.01 [4] so the spins cannot partake of the field energy $-\chi_a H^2/2$.

This scenario can also explain other observed features. The crossover around 150 K shown in Figs. 4 and 5(a) may be understood as a departure of the direction of the WF moments from perpendicular to the (ab) plane to a direction almost parallel to the b axis (see Fig. 1), where the XY anisotropy, weaker due to temperature fluctuations, ceases to play a decisive role. Physically, this corresponds to the fact that the conventional out-of-plane XY mode changes its nature as the WF moment rotates away from the c axis. Prompted by this idea, we calculated [solid lines in Fig. 4(c)] the spin-wave dispersions using

Eq. (1) in the extreme case of $\alpha = 0$ and a small DM gap which still confines the moments in the (bc) plane. Although finite temperature effects have to be taken into account, we note that this simple estimation qualitatively reproduces the experimental dispersions. We also comment on the possible relevance of our findings to the switch of orthorhombic axes in magnetic fields [7]. If a state similar to Fig. 1(d) is realized (which we show in Fig. 5 to persist to temperatures close to 300 K even for $x = 0.01$), then the magnetic force in an external field is significantly enhanced due to the net in-plane magnetic moment.

The qualitative scenario we propose leaves as open questions the finite Raman coupling to the FIM only for fields $\vec{H} \parallel \hat{b}$ and also the surprising observation of its temperature dependent spectral weight being peaked at T_N . However, if we assume that the FIM mode is an excitation other than the XY gap, arising, for instance, as a result of the four-sublattice structure, then the common interpretation of the excitation around 40 cm^{-1} found in several 2D layered AF's has to be reconsidered.

In summary, we discovered a field induced magnetically ordered phase in detwinned $x = 0$ and $0.01\text{ La}_{2-x}\text{Sr}_x\text{CuO}_4$. While the DM gap can be explained within the AF ordered state in the framework of Eq. (1), the behavior of the higher frequency field induced modes both above and below T_N requires an analysis outside of the traditional interpretation of low energy magnetic dynamics in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$.

We acknowledge useful discussions with A. N. Lavrov and M. V. Klein.

*Electronic address: gozar@lucent.com

†Electronic address: girsh@bell-labs.com

- [1] M. A. Kastner *et al.*, Rev. Mod. Phys. **70**, 897 (1998).
- [2] B. Keimer *et al.*, Phys. Rev. B **46**, 14 034 (1992).
- [3] R. Coldea *et al.*, Phys. Rev. Lett. **86**, 5377 (2001).
- [4] A. N. Lavrov *et al.*, Phys. Rev. Lett. **87**, 017007 (2001).
- [5] Y. Ando *et al.*, Phys. Rev. Lett. **88**, 137005 (2002).
- [6] Y. Ando, A. N. Lavrov, and S. Komiyama, Phys. Rev. Lett. **90**, 247003 (2003).
- [7] A. N. Lavrov, S. Komiyama, and Y. Ando, Nature (London) **418**, 385 (2002).
- [8] C. J. Peters *et al.*, Phys. Rev. B **37**, 9761 (1988).
- [9] P. A. Fleury and R. Loudon, Phys. Rev. **166**, 514 (1968).
- [10] T. Thio *et al.*, Phys. Rev. B **38**, 905 (1988).
- [11] Because Eq. (1) neglects the interplane interaction, it cannot be used to account for the region $\vec{H} \parallel \hat{c}$ ($H < H_{WF}$).
- [12] M. A. Kastner *et al.* Phys. Rev. B **38**, 6636 (1988).
- [13] B. Keimer *et al.*, Z. Phys. **91**, 373 (1993).
- [14] L. Shekhtman, A. Aharony, and O. Entin-Wohlman, Phys. Rev. B **47**, 174 (1993).
- [15] M. Matsuda *et al.*, Phys. Rev. B **65**, 134515 (2002).
- [16] A. Aharony *et al.*, Phys. Rev. Lett. **60**, 1330 (1990).
- [17] R. J. Gooding *et al.*, Phys. Rev. B **55**, 6360 (1997).
- [18] T. Thio *et al.*, Phys. Rev. B **41**, 231 (1990).